

Critical review on the physical and mechanical factors involved in tissue engineering of cartilage

Articular cartilage defects often progress to osteoarthritis, which negatively impacts quality of life for millions of people worldwide and leads to high healthcare expenditures. Tissue engineering approaches to osteoarthritis have concentrated on proliferation and differentiation of stem cells by activation and suppression of signaling pathways, and by using a variety of scaffolding techniques. Recent studies indicate a key role of environmental factors in the differentiation of mesenchymal stem cells to mature cartilage-producing chondrocytes. Therapeutic approaches that consider environmental regulation could optimize chondrogenesis protocols for regeneration of articular cartilage. This review focuses on the effect of scaffold structure and composition, mechanical stress and hypoxia in modulating mesenchymal stem cell fate and the current use of these environmental factors in tissue engineering research.

Keywords: articular cartilage osteoarthritis • chondrogenesis • differentiation • mesenchymal stem cells • tissue engineering

Osteoarthritis represents the most common form of over 100 types of arthritis and affects more than 124 million people worldwide. Damage from trauma, infection, autoimmune disorders or age produces inflammation in articular cartilage (AC), which worsens over time causing pain, swelling of joints and diminished range of motion. Because it impairs function, it creates a significant burden on society. The impact stems from the cost of radiographic diagnosis, palliative treatment, surgical procedures, loss of productivity and co-morbid diseases. Current treatment of osteoarthritis focuses on alleviating the symptoms. After the onset of osteoarthritis, existing therapies are unable to reverse or prevent the progression of the disease. In advanced cases with severe pain that do not respond to symptomatic treatments, surgical procedures such as autologous chondrocyte implantation (ACI) or joint replacement may be recommended [1,2].

Because the spontaneous repair process of cartilage is temporary and inefficient, defects

are often healed by the formation of fibrocartilage that is functionally inferior to the native hyaline cartilage [3]. Chondrogenesis, the processes by which cartilage is formed, is the result of a several steps orchestrated by signaling molecules [4–6], receptors, transcription factors [7], interaction of cells with the matrix [8] and other environmental factors. Mesenchymal stem cells (MSCs) are recruited and condense, beginning to proliferate and differentiate into a chondrogenic phenotype. This is followed by continued differentiation into mature chondrocytes during which they secrete cartilage-specific extracellular matrix (ECM) proteins such as type II collagen and aggrecan. Finally, unwanted terminal differentiation occurs when the chondrocytes become hypertrophic and bone tissue replaces the original cartilage. Control of the process of chondrogenesis is in damaged joints, these activities are not happening efficiently.

Encouraging advances in the field of stem cell research give hope for better options in

Carrie Gaut^{*1,2} & Kiminobu Sugaya³

¹INDICASAT-AIP, Ciudad de Saber, Clayton, Apartado 0843-01103, Panama, Rep. de Panama

²Department of Biotechnology, Acharya Nagarjuna University, Guntur, Andhra Pradesh 522510, India

³Burnett School of Biomedical Sciences, University of Central Florida College of Medicine, Orlando, FL 32827, USA

*Author for correspondence:

Tel.: +1 850 449 7301
cgaut4@yahoo.com

treating cartilage damage. Researchers attempt to bio-engineer cartilage for treatment of traumatic lesions where the healthy environment can support regeneration [9,10]. Stem cell or bioactive injectables are being tested for treating the more complicated pathogenesis of osteoarthritis [11–13]. For stem cell therapy to be effective and lasting, the aforementioned variables must be manipulated to achieve ideal conditions. Optimization of chondrogenesis relies on the appropriate combination of the different signals, the timing of those signals, concentration of required factors, mechanical stimulation, the upregulation and downregulation of specific genes through transcription factors and micro-RNAs [14], and the epigenetic modification of DNA via methylation and acetylation. The obstacle to effective stem cell transplantation therapies lies in getting the cells to differentiate and behave in the desired way, integrating and working with the host's other cells in a way that mimics native tissue. In order for stem cell-based tissue engineering of AC to be successful, a matrix surrounding the cells with the same mechanical and protective properties as native cartilage must be produced. The environment surrounding stem cells has a direct influence on how they differentiate, what signaling factors are utilized and which genes are activated or suppressed. Studies suggest that in addition to

signaling molecules, scaffolding properties, mechanical loading and oxygen availability play a key role in the differentiation process [15–22]. This review focuses on how scaffold structure and composition, mechanical stress and modification of oxygen availability modulates the differentiation of MSCs to mature chondrocytes and also how these stimuli affect gene expression. Understanding of these environmental effects and how to control them will help optimize chondrogenesis protocols used in tissue engineering.


Important mechanical properties of cartilage

The difficulty in tissue engineering of cartilage lies in the complexity of the tissue. Although it constitutes a very thin covering on the surface of bones in the synovial joints (2.21 mm in the human knee, for example), AC is quite diverse. It varies in thickness, cell density, matrix composition and mechanical properties within the same joint, different joints and among species [23]. It is typically divided into four zones: superficial zone, transitional zone/middle zone, deep zone and calcified cartilage zone. Chondrocytes within each zone differ in shape, size and orientation relative to the articular surface. They also differ in metabolic activity and respond differently to mechanical loading.

Chondrocyte–matrix interactions are essential for the maintenance of AC throughout life. The matrix protects chondrocytes from mechanical damage and helps them maintain shape and phenotype. Passing through and stored in the matrix are nutrients, substrates, synthesized molecules, degraded molecules, metabolic waste, cytokines and growth factors [24]. The movement of fluid and molecules depends in large part on the presence of large aggregating proteoglycans and how they are organized within the ECM.

AC demonstrates both viscous and elastic behavior when deformed. It affords a smooth, lubricated, low-friction surface during movement and assists in load transmission to the subchondral bone. AC can withstand high cyclic loads with little to no damage or degeneration [25,26]. The combination of frictional resistance to water flow and water pressurization within the matrix provides the two main mechanisms in which AC is able to endure substantial loads, often several times one's bodyweight. Joint motion and load are essential in maintaining proper AC structure, function and metabolism. Inactivity can actually lead to deterioration of cartilage [27].

Aggrecan, the largest and most abundant proteoglycan in AC, occupies the interfibrillar space of cartilage ECM and gives cartilage its osmotic properties – vital to its capacity to oppose compressive loads [27]. In an aqueous environment, proteoglycans have negatively charged sites that repel each other causing it to spread

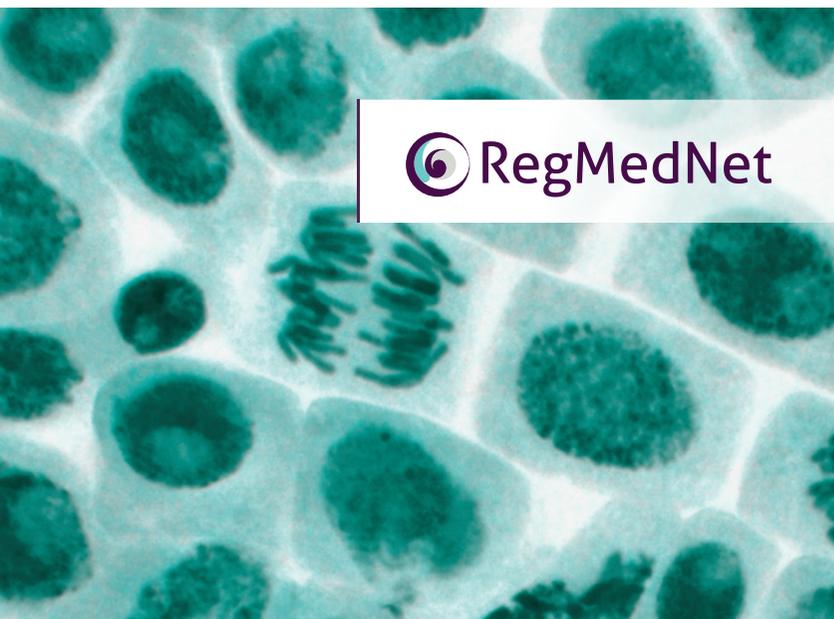

 RegMedNet

BRIDGE THE GAP

Collaborate and share insights through
blogs and videos

Join today

www.RegMedNet.com



out and take up more space in the ECM. Volume is limited by the entrapment of the aggregates in the collagen fiber network. When cartilage is compressed, the negatively charged sites on the aggregated proteoglycans are pressed together, which intensifies their repellant force and contributes to the compressive stiffness of cartilage [28].

Mechanical response of AC also depends on flow of fluid through the tissue and across the articular surface. Average surface pore size of AC is 6.0 nm, which allows water, oxygen, glucose and ions to move through, but hinders movement of the larger macromolecules such as hyaluronan and aggrecan. Under rapidly applied loads, there is not enough time for fluid flow and cartilage behaves as a single-phase, incompressible, elastic solid [28]. Under less rapid distortions, fluid can flow out of the AC and then back in once the force is removed. Under constant loads, the viscoelasticity of AC is time-dependent as fluid can initially move through the tissue more quickly followed by a slowing down as the force continues, the tissue stiffens and friction increases until the tissue reaches equilibrium [27]. The most compliant and viscous part of AC, the transitional zone, may be the most critical for dissipating energy and protecting the joint from damage [29]. Regardless of the type of load, fluid pressure is a major factor of total load support ability of AC because it reduces stress on the ECM.

Main components in cartilage tissue engineering

Tissue engineering has become synonymous with regenerative medicine. Broadly described as the manipulation of cells, biochemical factors, physical factors and biological engineering materials, the goal is to maintain, recover or replace biological functions. To repair cartilage defects like those found in osteoarthritis, tissue engineers must first determine and acquire the appropriate cell types for cartilage and bone regeneration. Embryonic stem cells are pluripotent and can form tissues from any of the three germ layers (endoderm, mesoderm and ectoderm). Ethical and safety debates over the use of ESCs caused a shift in attention to the use adult stem cells, which are limited to differentiating into the cell types of their origin tissue. MSCs are a type of multipotent adult stem cell with the ability to generate bone, muscle, cartilage, fat and other related tissues. Studies show MSCs improve the regeneration process mainly by releasing paracrine, or growth factors [30]. They can be isolated from a variety of tissues including peripheral blood, bone marrow, tooth pulp and adipose tissue [31–33]. In conjunction with their multipotency, they have a large capacity for self-renewal and therefore show huge

promise for use in tissue repair. In addition, MSCs are nonimmunogenic and can be used in autologous or allogeneic transplant procedures. Induced pluripotent stem cells (iPSCs) are genetically reprogrammed adult stem cells, which behave like ESCs. They are currently useful tools in drug development and disease modeling and they are promising for tissue engineering. Cocultures of chondrocytes and MSCs are another possibility for regenerative efforts as stem cells may be able to catalyze chondrocytes to produce new tissue via paracrine signaling [34,35].

In addition to choosing a suitable cell type for tissue engineering of AC, scientists must decide how to encourage the proliferation and differentiation of the cells. During development, cartilage formation is strictly regulated by cellular interactions with the surrounding matrix, growth and differentiation factors, and environmental factors that activate or deactivate signaling pathways and spatiotemporal gene transcription. In adulthood, signaling factors regulate the various stages of chondrogenic differentiation. Certain bone morphogenic proteins help promote a chondrogenic phenotype [5,6]. TGF- β stimulates synthesis of ECM and begins the signaling cascade that activates gene expression of Sox9, a transcription factor known to be necessary for early chondrogenesis [7,36]. Conditioning with TGF- β 1 and TGF- β 3 enhances terminal differentiation of MSCs undergoing chondrogenesis [37]. Sox9 is necessary to activate gene promoters of collagen type II, aggrecan and other important cartilage-building proteins [38]. Sox9 inhibits activation of the Wnt/ β -catenin pathway that drives hypertrophic differentiation and leads to calcification [39]. IGF and FGF are also necessary for proper differentiation to mature chondrocytes [36,40], enhancing type II collagen and glycosaminoglycan (GAG) production. Factors can be added individually; however, many times joint delivery of several factors is more beneficial. For example, delivering IGF-1 and FGF-2 together results in low expression of fibrocartilage and hypertrophic markers [41].

Two methods dominate tissue engineering's use of MSCs:

- *Ex vivo* differentiation: after MSC isolation and expansion, cells are seeded onto scaffolds where they are matured using bioactive and chemical factors, as well as biomechanical stimuli. The cell-seeded scaffold could then be surgically implanted at the damage site [42–44]. This is a less than ideal approach due to the invasiveness of the implantation procedure. In addition, progress is limited by the tendency for chondrocytes to move toward terminal hypertrophy and produce calcified tissue [45–47];

Table 1. Scaffold biomaterials used for recent cartilage tissue engineering studies.

Natural scaffold materials	Ref.	Synthetic scaffold materials	Ref.
Collagen	[63,103,104]	Poly(ethylene) glycol	[61,105]
Chitosan	[106,107]	Gelatin-hydroxyphenylpropionic acid	[71]
Fibrin	[54,56,108,109]	Poly(caprolactone)	[110,111]
Alginate	[53,64]	Self-assembling peptides	[68,70,72,73]
Hyaluronic acid	[55,64,108]	poly(L-lactic acid)	[67,111]
Agarose and gellan gum	[56]	Polyurethane	[60,109,112]
Decellularized cartilage matrix	[57,58]	Polyvinyl alcohol-methacrylate	[59]

Various biomaterials have been used in attempts to optimize chondrogenesis and create tissue-engineered cartilage with the organization and mechanical properties of native articular cartilage.

- *In vivo* differentiation: a second approach is to inject harvested MSCs directly into the area of defect. There, the MSCs' regenerative functions (immune suppression, anti-inflammatory effects, soluble factors etc.) can work toward tissue restoration [48–50]. Intra-articular injections of MSCs by themselves provide short-term relief, however, they may or may not provide the long-term healing of cartilage defects desired in tissue repair [51,52] due to the migratory nature of the MSCs.

Effective scaffolding properties for tissue engineering of cartilage

For successful cartilage tissue engineering, biomaterial scaffolds must support the survival and differentiation of cells used. This is done via the basic properties of the material and also explicit cues built into the scaffold. Pore size and rigidity must be taken into account, as well as a 3D architecture that allows cell adherence, limits migration and encourages formation of hyaline-like tissue. Mechanical, lubricating and swelling properties must also be considered for cartilage tissue engineering. In an effort to provide all these properties, many different types of biomaterials have been tested as scaffolds: natural and synthetic polymers, hydrogels, decellularized scaffolds and nanofiber-based scaffolds. Table 1 lists some of the scaffolding biomaterials used in recent studies on cartilage tissue engineering. Efforts focus on providing an environment for cell attachment and growth that will encourage the cells to form a specific tissue type.

Natural & synthetic scaffolds

Natural biomaterial scaffolds include those made from proteins, such as collagen, fibrin and silk, as well as those made from polysaccharides such as alginate, hyaluronic acid (HA) and chitosan. Natural polymers are useful because they are biologically active and usually foster cell adhesion, proliferation and growth. In addition, they are biodegradable and, therefore, allow host cells to produce their own ECM to replace the scaffold as it

degrades. MSCs seeded onto natural scaffolds tend to have high synthesis of cartilage structural components such as collagen II, aggrecan and GAGs, especially in the presence of cartilage-specific growth factors [53–55]. Although natural polymers do not interfere with differentiation and allow for high metabolic activity of host cells, it remains difficult to create the necessary macro- and microarchitecture that encourages formation of hyaline-like cartilage [56]. In addition, they do not provide the mechanical strength necessary to mimic native AC [54]. Another promising natural biomaterial used in tissue engineering is decellularized cartilage matrix. Although availability of this scaffold material is limited, use of cartilage grafts allow the collagen ultrastructure to remain intact and does not compromise the mechanical function or integrity of the tissue. Furthermore, it has a chondroinductive effect on cells *in vitro* [57,58].

Synthetic scaffolds afford an alternative to natural material scaffolds and include polymer-based and peptide-based biomaterials. Synthetic biomaterials as scaffolding provide the advantage of reproducibility and control over scaffold properties such as cross-linking density and degradation rate. The ability to adjust pore size and stiffness of the matrix allows for better stability and regulation of mechanical properties as well as better cell adhesion and motility [59–61]. Drawbacks to synthetic scaffolds include the risk of rejection once implanted as well as by-products formed during degradation that may negatively influence the cells and surrounding tissue [62].

Composite scaffolds

Scaffolds fabricated from two or more materials can help circumvent some of the problems found with single-phase biomaterials. Studies have combined natural polymers [63,64] as well as mixing natural and synthetic polymers [65]. Composite scaffolds allow for the creation of more complex geometries and better functional properties more representative of AC in order to support enhanced cell adhesion, proliferation and dif-

ferentiation [60,64]. Embedding fibers can reinforce the scaffold and improve mechanical strength and function [59]. Layered composite scaffolds have the potential to better mimic the zonal characteristics of native tissue [22,66]. 3D woven composite scaffolds may better recreate the biomechanical behavior of cartilage tissue [65]. More recently, nanostructured composite scaffolds are promising for tissue engineering due to their biomimetic mechanical features and physiochemical properties [60,67,68]. Because collagen fibers in the diameter range of 500–500 nm comprise the bulk of ECM, a nanotopographical approach to tissue engineering might better allow synthesis of tissues with complex geometric organizations. MSCs respond to changes in density of nanotopographical cues by regulating their internal cytoskeletal network and mechanical changes guide them to make cell fate decisions [69]. Composite synthetic scaffolds permit the creation of directionally dependent load support similar to native cartilage collagen ultrastructure and with an equilibrium coefficient of friction similar to native AC [65]. However, achieving the scale and organization of native AC has so far been unsuccessful.

Hydrogels

Because hydrogels can be developed with mechanical, lubricating and swelling properties similar to that of native AC, they are often used in attempts to engineer

cartilage. In addition, hydrogels are tunable – parameters such as polymer composition and cross-linking density can be manipulated [70,71]. Another benefit is that they are injectable. Hydrogels can be made with natural or synthetic polymers. Natural polysaccharide-based hydrogels, such as hyaluronan, chitosan, agarose and alginate, are intrinsically biocompatible but do not encourage cell attachment [56]. The lack of attachment makes these choices less attractive for 3D scaffolds used in cartilage repair efforts. In contrast, natural protein-based scaffolds, including collagen, fibrin and silk, promote cell-to-surface binding. Self-assembling peptide hydrogels can create precise arrangements approximating the micro- and nano-characteristics of natural ECM, which also allow for regulation of mechanical properties and stability. In addition, they can be used to dispense chondrogenic factors to encapsulated MSCs [72,73]. These properties, in turn, increase cell adhesion, proliferation and migration of cells. Synthetic hydrogels, such as poly(ethylene glycol) and poly(vinyl alcohol), can promote cell adhesion indirectly through surface modifications that improve cell seeding and anchorage [74,75]. Synthetic hydrogels are some of the most easily tunable biomaterial scaffolds allowing for research on macrostructure variations.

In order for a biomaterial scaffold to be useful for *in vivo* tissue engineering, cells must adhere to the scaffold surface and be able to survive, differentiate

Table 2. Effect of scaffold properties on mesenchymal stem cell chondrogenesis.

Property	Effects seen	Ref.
Pore size	300 μm mean pore size induced higher chondrogenic gene expression than smaller mean pore size (94 or 130 μm)	[113]
Geometry	Interpenetrating polymeric network scaffold has higher expression levels of chondrogenic markers	[64]
	Greater chondrogenic gene expression in polyurethane scaffolds with excellent porosity and good pore interconnectivity	[112]
	Scaffold alignment is sufficient to drive MSC differentiation without additional chemical stimuli	[15]
Adhesivity	Lower RGD densities enhance chondrogenesis	[114]
Rigidity	Lower stiffness gels lead to higher mRNA levels of chondrogenic markers (<i>Col2a1</i> , <i>Agc</i> and <i>Sox9</i>)	[115]
	Increased cross-linking promotes hypertrophic differentiation of chondrogenically induced MSCs	[116]
	Lower cross-linked matrix yields increase percentage of cells with chondrocytic morphology	[117]
Degradation rate	MSCs encapsulated in MMP-sensitive but hydrolytically stable hydrogels have a more spreaded morphology, express higher levels of chondrogenic marker genes and lower levels of hypertrophic genes compared with MMP-insensitive hydrogels	[118]

Various scaffolding properties can be manipulated to enhance chondrogenesis.
MSC: Mesenchymal stem cell.

and produce matrix. A functional biomaterial scaffold must provide a framework for the growth of the desired tissue and allow for organization and cellular communication. Table 2 summarizes the effect of various scaffold properties on chondrogenesis of MSCs. The biomaterial must also afford a smooth, lubricated low-friction surface during movement and assist in load transmission to the subchondral bone. Porous scaffolds engineered with bioactive factors and peptides common to the ECM of AC can help promote differentiation as well as improve cell attachment function. Engineered hydrogels can have similar mechanical properties to AC. Micro- and nanopatterned scaffolds are attractive options because of the high degree of control over geometry, adhesiveness and stiffness of the scaffold, which influences cell patterning and differentiation. 3D scaffolds tend to influence cell migration and lead to higher expression levels of differentiation-associated transcription factors, such as Sox9. While various scaffolds may be able to support healthy cartilage formation, mimicking the mechanical properties and resiliency of AC has eluded researchers thus far. Scaffolds will need to initially support joint loads and then gradually degrade as the developing cartilage forms. Future studies for tissue engineering of AC will most likely focus on unique, 3D, nanopatterned scaffolds that can be formulated to stimulate migration, differentiation and organization of MSCs in order to mimic the composition of the various layers in native AC. To prevent further damage from invasive implantation procedures, bioinjectable scaffolds are also at the forefront of tissue engineering research. For patients with articular defects, the eventual goal of cartilage tissue engineering is a return to normal joint function by redevelopment of healthy AC. The new cartilage must integrate with existing cartilage and the underlying bone. Cell-based techniques that utilize supportive biomimetic scaffolding along with growth factors and other environmental signals hold the greatest promise for advances in the clinical application of tissue engineering.

Use of mechanical stimulation in tissue engineering of cartilage

Everyday use puts joints under various types of stresses and strains. The motion and loading of synovial joints is necessary for the proper structure, function and metabolism of native AC. Mechanical stress includes hydrostatic pressure, dynamic and static compression, rotation and shear. AC possesses low permeability and as such, hydrostatic pressure in the interstitial fluid governs the natural environment of chondrocytes during joint loading [76]. Compression of AC tissue occurs naturally during everyday movements such

as rising from a chair or climbing stairs. Rotation is the gyration of a bone around its central axis. Shear strain occurs when tissue layers are shifted laterally in relation to each other, such as when the knee is in a flexed position and then twisted. When present in the chondrocyte environment, these forces can affect cellular metabolism and help distribute nutrients and oxygen. *In vitro* mechanical stimuli encourage chondrogenic cells to differentiate and produce matrix, which enhances cartilage formation [77,78]. During joint loading, chondrocytes will deform, losing cellular height and volume, and then show a complete recovery after the compressive force is removed [79,80]. Forces that modify the cell and nucleus structure of chondrocytes correlate with local changes in aggrecan synthesis as well as type I and II collagen, proteoglycan 4 and collagen X [81,82]. Mechanical stimuli can induce calcium signaling, which triggers various metabolic and signaling activities [83]. Loading allows chondrocytes to regulate actin cytoskeleton dynamics and organization by changing gene expression for associated proteins [84,85].

There are multiple regulatory pathways chondrocytes use to detect and respond to stimuli. Upstream signaling pathways may lead to changes in transcription, translation, post-translational modification, extracellular assembly and ECM degradation [17,21,77,86–88]. The various forces and flows that occur during mechanical loading act in parallel with released cytokines and growth factors to regulate chondrocyte homeostasis [80]. Once in the ECM, these molecules can bind to receptors on cell surfaces in order to stimulate cellular activity or become trapped in the ECM. The activation and inhibition of these cascades and all the molecules involved are still under investigation and not completely understood; however, due to the nature of AC, a certain amount of mechanical stimulation is necessary for proper functioning of the tissue and cells. With that in mind, many studies have been undertaken *in vitro* to determine the types and frequencies of mechanical stimulation that will induce MSCs to produce functionally equivalent cartilage. Table 3 lists the effects of various loading protocols on matrix production and differentiation.

Several studies have looked into the signaling pathways involved in mechanical stimulation of stem cell proliferation and differentiation. A recent investigation discovered that the ERK1/2 pathway determines whether MSCs differentiate toward an osteogenic or chondrogenic fate. In the absence of these pathways, human bone marrow-derived stem cells (BMSCs) in a fibrin gel scaffold stimulated by dynamic compression experience a downregulation of aggrecan and Sox9 and an upregulation of osteogenic markers such as osteo-

	Loading protocol	Environment	Effect	Ref.
Hydrostatic pressure	Cyclic, 10 MPa at 1 Hz, 4 h/day, 14 days	TGF- β 3	Upregulation of Sox9 and sGAG synthesis; downregulation of prehypertrophy and terminal differentiation genes <i>Ihh</i> and type X collagen	[119]
	Intermittent, 5 MPa at 0.5 Hz, 4 h/day, 7 days	Chondrogenic medium	Higher expression of aggrecan, Sox9 and type II collagen	[120]
	Dynamic vs static, 14–36 kPa at 0.25 Hz, 1 h/day, up to 7 days	TGF- β 1 prior to loading	Dynamic loading yielded stronger ECM and type II collagen staining; GAG secretion increased; elevated mRNA levels of type II collagen, aggrecan and Sox9	[121]
Compression	10% dynamic strain superimposed on static 2% tare strain, unconfined, 0.01–1 Hz, 1–4 h/day, 3–6 weeks	TGF- β 3	Improved distribution of proteoglycans and collagens; modulation of many chondrogenesis-associated genes (413 upregulated and 139 downregulated)	[89]
	Dynamic, 10% strain at 1 Hz, 1 h/day for up to 21 days	TGF- β 3 prior to loading	Gene expression of aggrecan and collagen type II in construct core increased at 7 and 21 days, but in the annular region at day 14 and 21	[90]
	Sinusoidal, 10–40 kPa at 0.5 Hz, 1 h/day, up to 14 days	Loading after chondrogenic induction	Increase in gene expression of <i>Col2a1</i> and <i>Ihh</i>	[93]
Pressureless	Cyclic, external magnetic field, 30 min every 1.5 h, 8 h/day, up to 3 weeks	With and without chondrogenic medium	GAG deposition; chondrogenesis confirmed by immunostaining of aggrecan, type II collagen and Sox9	[91]
Multifactorial bioreactors	Cyclic, compression and interfacial shear at 1 Hz, 1 h/day, 5 days/week, for 3 weeks	Fibrin-polyurethane scaffolds	Cellularity of scaffold increased; deposition of sulfate-rich GAG at top surface of scaffold	[109]
	Dynamic, compression and rotation for 2–4 weeks vs unloaded culture	Third passage cells seeded on fibrin-polyurethane scaffolds	Loading significantly higher in mRNA expression of type II collagen, aggrecan and COMP. Load after unload protocol also increased superficial zone protein.	[122]
	Dynamic, compression and shear for 2–4 weeks vs unloaded culture	Cultured within polyurethane scaffold rings	Loading maintained chondrogenic mRNA expression of collagen type II, aggrecan and COMP	[123]

Various loading regimens have been used for the study of mechanical stress in tissue engineering efforts.
ECM: Extracellular matrix; GAG: Glycosaminoglycan.

calcin, alkaline phosphatase and collagen type I [92], demonstrating a tendency to move toward bone rather than cartilage formation. Another investigation explored the effect of dynamic compression on cell viability during chondrogenesis of rat BMSCs, as well as the underlying mechanisms involved. They found that inhibiting bone morphogenic protein signaling decreased cell viability, but application of dynamic stress was somewhat able to offset the reduction [93].

Transduction of mechanical stimulation into chemical signals seems to play an important role in the proliferation and differentiation of MSCs into a chondrogenic phenotype. Determining the optimal frequency, type and timing of mechanical loading on

cultures for tissue engineering remains a significant challenge. Which signaling pathways are activated in response to mechanical loading is also important (Figure 1). Current research suggests several things. First, mechanical stimulation can be effective in the differentiation of MSCs after a time of preconditioning with exogenous growth factors. Second, the response of differentiated MSCs to mechanical stimulation has a positive effect on ECM remodeling. Finally, the development of bioreactors that can provide a combined, dynamic loading regimen more similar to the native stresses AC endures may lead to enhanced chondrogenesis in tissue-engineered constructs.

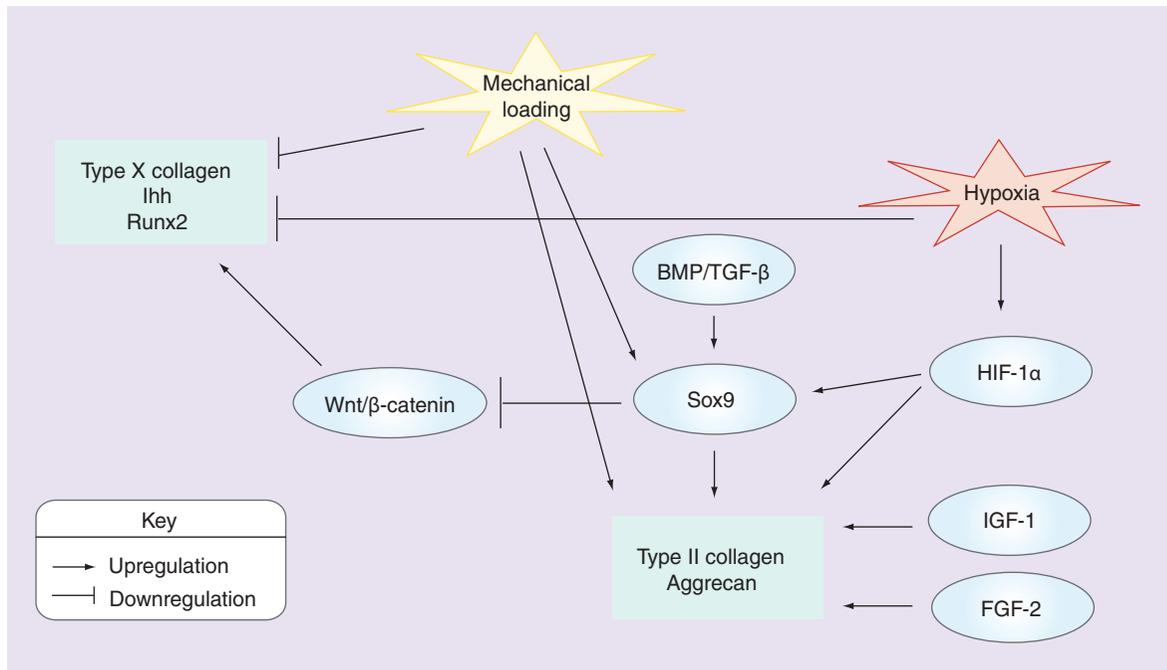


Figure 1. Signaling pathways modulating mRNA expression of chondrogenic genes. Both moderate hypoxia and mechanical loading inhibit pathways leading to hypertrophy and osteogenesis while stimulating the production of cartilage-building proteins.

Effect of hypoxia on AC differentiation of MSCs

Since AC is avascular, oxygen levels within the AC are lower than many other tissues and oxygen levels vary by depth. The superficial zone receives oxygen from contact with the synovial fluid and maintains an oxygen level between 6 and 10%. The deep zone, which has minimal oxygen from the vascularized subchondral bone, has an oxygen level around 2% [94]. Chondrocytes are adapted to this oxygen-poor environment; in healthy AC, they maintain their phenotype and produce the necessary ECM and macromolecules for proper function. This is mainly achieved through the effects of HIF-1 α , an oxygen-sensitive transcriptional activator. During embryogenesis when there are continuing changes in oxygen concentrations, HIF-1 is necessary for proper development and survival of the embryo. *In vitro* studies show it is a necessary transcription factor for the hypoxic induction of chondrogenesis [53]. Observations of cartilage that lacks HIF-1 α show massive cell death in the central regions suggesting that HIF-1 α is necessary for survival and differentiation of chondrocytes in hypoxic conditions by helping to maintain a balance between oxygen availability and handling in developing growth cartilage [95]. Adaptation may possibly also depend on the composition of the surrounding ECM [96]. For effective tissue engineering of cartilage, the effects of hypoxia on chondrogenesis must be better understood. Much research has been done to determine the influence that changing oxygen tension has on the

proliferation and differentiation of MSCs from a variety of sources.

Studies suggest culturing MSCs *in vitro* under moderately hypoxic conditions (5% O₂) is beneficial to achieving a chondrogenic phenotype, expression of chondrogenic transcription factors, suppression of osteogenic transcription factors, synthesis of ECM and production of type II collagen (Figure 1). One study found that when compared with culturing in normoxic conditions (20–21% O₂), hypoxic conditions suppressed the osteogenic differentiation potential of human adipose-derived MSCs (ADSCs) without affecting overall protein production and cell viability. Calcium deposition decreases and there is a reduction in Runx2 and osteocalcin (two key osteoblast-related genes) mRNA levels in low oxygen. They observed that hypoxia supports earlier collagen II mRNA expression as well as its later production within the matrix [97], which is good for AC formation. Another study shows human ADSCs differentiated in 5% oxygen tension demonstrate increased cellularity and matrix deposition that organizes itself in a zonal manner and exhibits cartilage-like morphology [98]. Human BMSCs cultured under 5% oxygen conditions in alginate show downregulation of osteogenic transcription factors, Cbfa1 and Runx2, stronger reduction of fibrocartilage and hypertrophic cartilage expression, as well as increased mRNA expression of collagen type II and aggrecan, increased protein level-expression of procollagen II protein and sulfated GAGs, as well as upregulation of Sox transcription factors (L-Sox5, Sox6

and Sox9). They found this to be true *in vitro* and *in vivo* with no serum or growth factors used [53]. *In vitro* low-oxygen preconditioning of rabbit adipose stromal cells also leads to significantly greater expression of type II collagen and aggrecan [99]. Bovine articular chondrocytes and BMSCs cultured in 3D scaffolds under 5% hypoxia show an increased collagen type II to collagen type I ratio and decreased cellularity as well as increased matrix synthesis in early cultures [35]. When culturing in a 3D environment, hypoxia may significantly suppress human MSC hypertrophy and calcification [96].

Studies that considered both the MSC expansion process and the differentiation process, found that the timing of oxygen deprivation is important. According to one study, preconditioning BMSCs in 5% O₂ may enhance clonogenicity but impair differentiation. They recommend expansion in normoxia followed by hypoxia during differentiation to enhance *in vitro* chondrogenesis [100]. Another study using dermis MSCs confirmed that continuous hypoxic conditions (5% O₂) decreases the collagen type II to total collagen ratio; however, differentiation in hypoxic conditions following normoxic expansion increases production of collagen type II and GAGs. In that same study, expansion in hypoxia increased total matrix production [101]. Yet another study suggests that hypoxia alone has no effect on chondrogenesis or matrix synthesis, but that the effect is dependent on the hydrogel-scaffolding properties [96].

Culturing in extreme hypoxic conditions produces varying results. One study found that 1% O₂ conditions decrease mRNA levels of Runx2, decrease expression of type X collagen and enhance chondrogenesis in human BMSCs by yielding higher mRNA levels of Sox9, type II collagen and aggrecan, increasing proteoglycan synthesis and increasing type II collagen expression. The research reveals that extreme hypoxic culture activates the PI3K/Akt/FoxO pathway that suppresses caspase activation of chondrogenesis-induced apoptosis in MSCs [16]. Another study found that severe hypoxia decreases gene expression to the point that it halts all differentiation [102].

Because cartilage is naturally a low-oxygen environment, it makes sense that hypoxia might play a significant role in the development of tissue-engineered cartilage. Hypoxic-based culturing protocols fluctuate between the different research experiments. Dissimilarities in cell sources, culture conditions and oxygen-deprivation timing make a direct comparison of hypoxia studies difficult. These variations limit optimization of the expansion and differentiation process and may hinder rapid advancement of the field toward clinical applications. However, the majority of research supports the application of a low-oxygen culture envi-

ronment around 5% during the *in vitro* differentiation process to promote chondrogenesis.

Conclusion

Osteoarthritis causes a huge societal burden and there is no known cure. Pharmaceuticals can help alleviate pain and delay deterioration, but cannot restore the damaged tissue. AC is a complex layered environment and the spontaneous repair process is inefficient resulting in production of inferior fibrocartilage without the strength and resiliency of native hyaline cartilage. Advances in regenerative medicine, specifically stem cell knowledge and tissue engineering techniques, have made progress in repairing and replicating AC. The goal in stem cell chondrogenesis is to find a cell source that can be directed to produce new cartilage capable of functioning efficiently in stressful joint environments. The use of MSCs in tissue engineering efforts shows great promise due to their availability, immunosuppressive characteristics and paracrine signaling.

Promotion of MSC chondrogenesis is achieved using many different strategies. Addition of chondrogenic growth factors individually or in combination helps direct the cell toward a chondrogenic fate. However, growth factors alone are not enough to recreate AC tissue. The stem cell environment has a direct influence on how they differentiate. The employment of 3D scaffolds provides sites for cell attachment, helps direct migration and allows for control of pores size, geometry, adhesivity and stiffness, which help mimic the mechanical properties of AC. Mechanical stimulation in conjunction with exogenous growth factors directs MSC differentiation and assists with ECM remodeling. The use of multifactorial bioreactors capable of creating the combined stresses similar to normal joint loading seems promising. Oxygen being sensed by the cells depends on fac-

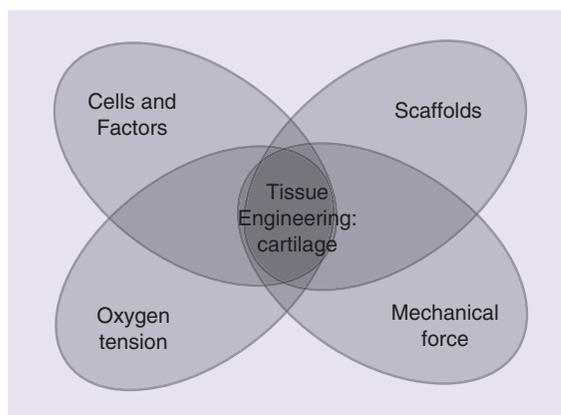


Figure 2. Important variables to consider for tissue engineering of cartilage. Placing cells in an environment with the appropriate signals and a scaffold on which to grow may hold the most promise articular cartilage regeneration.

tors that are hard to control, most importantly, level of medium and density of cells. However, hypoxic culture conditions of around 5% O₂ promote chondrogenesis of MSCs and should be considered when conducting future *in vitro* tissue engineering research.

Current technology has been unable to successfully regenerate cartilage with the appropriate structure, viscoelastic properties, ECM organization and biological activity. However, to date, no studies have dealt with all of these factors together (Figure 2). Increased experimentation with various biomaterials and cues, knowledge of how mechanical factors influence stem cell fate and manipulation of hypoxia-induced pathways will enhance AC tissue engineering efforts. To avoid surgical implantation issues, it would be ideal to develop injectable biomaterials that form a scaffold internally and provide a place for cells and factors to be implanted at the defect site. Mechanical stimulation and oxygen deprivation could then occur naturally in the joint.

Future perspective

For advancement of cartilage engineering, future studies cannot focus on only one or two variables, but must look at the bigger picture. Noninvasive stem cell techniques that trigger the body into healing more completely are effectively the wave of the regenerative future. Many stem cell procedures are available internationally, but the US FDA currently limits how they are used in the USA. Autologous stem cell procedures require a significant amount of cells, which necessitates amplification of harvested cells. This requires a current Good Manufacturing Practice facility. Allogenic sources such as amniotic

membrane may be the safest and simplest way to improve joint function in the future. Already used for wound healing and in the treatment of plantar fasciitis, cryopreserved chorion-free amniotic membrane preserves all tissue components, including the 3D tissue matrix architecture, growth factors and MSCs. Much progress has been made in the field of regenerative medicine. Well-designed clinical trials, rigorous evaluation of engineered tissue and methods for assessing successful outcomes will be very important in the quest for engineered cartilage that truly mimics healthy AC and restores damaged joints.

Acknowledgements

The authors would like to acknowledge Jagannatha Rao and Rubén Berrocal for their guidance, suggestions, proofreading skills and general support of this project.

Financial & competing interests disclosure

The authors have no relevant affiliations or financial involvement with any organization or entity with a financial interest in or financial conflict with the subject matter or materials discussed in the manuscript. This includes employment, consultancies, honoraria, stock ownership or options, expert testimony, grants or patents received or pending, or royalties.

No writing assistance was utilized in the production of this manuscript.

Open access

This work is licensed under the Creative Commons Attribution-NonCommercial 3.0 Unported License. To view a copy of this license, visit <http://creativecommons.org/licenses/by-nc-nd/3.0/>

Executive summary

Background

- When engineering cartilage with stem cells, scaffold structure and composition, mechanical loading and oxygen availability play a key role in the differentiation process.

Important mechanical properties of cartilage

- The diverse composition and organization of articular cartilage make it difficult to reproduce with current tissue engineering strategies.

Main components in cartilage tissue engineering

- Current cartilage tissue engineering efforts are not totally successful and the various methods using mesenchymal stem cells (MSCs) still have several drawbacks.

Effective scaffolding properties for tissue engineering of cartilage

- For successful cartilage tissue engineering, biomaterial scaffolds must support the survival and differentiation of the cells used via the basic properties of the material and also explicit cues built into the scaffold.

Use of mechanical stimulation in tissue engineering of cartilage

- Transduction of mechanical stimulation into chemical signals plays an important role in the proliferation and differentiation of MSCs into a chondrogenic phenotype.

Effect of hypoxia on articular cartilage differentiation of MSCs

- Mimicking the low-oxygen environment of articular cartilage during the *in vitro* MSC differentiation process promotes chondrogenesis.

Conclusion & future perspective

- In the future, allogenic sources of stem cells that can be directly injected may be the safest and simplest way to improve joint function.

References

Papers of special note have been highlighted as:

• of interest; •• of considerable interest

- 1 Gomoll AH, Filardo G, De Girolamo L *et al.* Surgical treatment for early osteoarthritis. Part I: cartilage repair procedures. *Knee Surg. Sports Traumatol. Arthrosc.* 20(3), 450–466 (2012).
- 2 Mcdermott I. Meniscal tears, repairs and replacement: their relevance to osteoarthritis of the knee. *Br. J. Sports Med.* 45(4), 292–297 (2011).
- 3 Danisovic L, Varga I, Polak S. Growth factors and chondrogenic differentiation of mesenchymal stem cells. *Tissue Cell* 44(2), 69–73 (2012).
- 4 Spater D, Hill TP, O’Sullivan RJ, Gruber M, Conner DA, Hartmann C. Wnt9a signaling is required for joint integrity and regulation of Ihh during chondrogenesis. *Development* 133(15), 3039–3049 (2006).
- 5 Jin EJ, Lee SY, Choi YA, Jung JC, Bang OS, Kang SS. BMP-2-enhanced chondrogenesis involves p38 MAPK-mediated down-regulation of Wnt-7a pathway. *Mol. Cells* 22(3), 353–359 (2006).
- 6 Karamboulas K, Dranse HJ, Underhill TM. Regulation of BMP-dependent chondrogenesis in early limb mesenchyme by TGFbeta signals. *J. Cell Sci.* 123(Pt 12), 2068–2076 (2010).
- 7 Tew SR, Clegg PD. Analysis of post transcriptional regulation of SOX9 mRNA during *in vitro* chondrogenesis. *Tissue Eng. Part A* 17(13–14), 1801–1807 (2011).
- 8 Acharya C, Yik JH, Kishore A, Van Dinh V, Di Cesare PE, Haudenschild DR. Cartilage oligomeric matrix protein and its binding partners in the cartilage extracellular matrix: interaction, regulation and role in chondrogenesis. *Matrix Biol.* 37C, 102–111 (2014).
- 9 Brochhausen-Delius C. Prostaglandin E₂: innovative approaches for tissue engineering of articular cartilage. *Pathologie* 35(Suppl. 2), 264–270 (2014).
- 10 Filardo G, Kon E, Di Martino A *et al.* Is the clinical outcome after cartilage treatment affected by subchondral bone edema? *Knee Surg. Sports Traumatol. Arthrosc.* 22(6), 1337–1344 (2014).
- 11 Jo CH, Lee YG, Shin WH *et al.* Intra-articular injection of mesenchymal stem cells for the treatment of osteoarthritis of the knee: a proof-of-concept clinical trial. *Stem Cells* 32(5), 1254–1266 (2014).
- **Clinical trial results that support use of intra-articular injections of mesenchymal stem cells for treatment of patients with osteoarthritis.**
- 12 Koh YG, Choi YJ, Kwon SK, Kim YS, Yeo JE. Clinical results and second-look arthroscopic findings after treatment with adipose-derived stem cells for knee osteoarthritis. *Knee Surg. Sports Traumatol. Arthrosc.* 23(5), 1308–1316 (2015).
- **Two-year postoperative results from intra-articular injections on elderly patients with knee osteoarthritis show improvement in pain and cartilage status.**
- 13 Vilar JM, Batista M, Morales M *et al.* Assessment of the effect of intraarticular injection of autologous adipose-derived mesenchymal stem cells in osteoarthritic dogs using a double blinded force platform analysis. *BMC Vet. Res.* 10, 143 (2014).
- 14 Yan C, Wang Y, Shen XY *et al.* MicroRNA regulation associated chondrogenesis of mouse MSCs grown on polyhydroxyalkanoates. *Biomaterials* 32(27), 6435–6444 (2011).
- 15 Subramony SD, Dargis BR, Castillo M *et al.* The guidance of stem cell differentiation by substrate alignment and mechanical stimulation. *Biomaterials* 34(8), 1942–1953 (2013).
- 16 Lee HH, Chang CC, Shieh MJ *et al.* Hypoxia enhances chondrogenesis and prevents terminal differentiation through PI3K/Akt/FoxO dependent anti-apoptotic effect. *Sci. Rep.* 3, 2683 (2013).
- 17 Kang MN, Yoon HH, Seo YK, Park JK. Effect of mechanical stimulation on the differentiation of cord stem cells. *Connect. Tissue Res.* 53(2), 149–159 (2012).
- 18 Jurgens WJ, Lu Z, Zandieh-Doulabi B, Kuik DJ, Ritt MJ, Helder MN. Hyperosmolarity and hypoxia induce chondrogenesis of adipose-derived stem cells in a collagen type 2 hydrogel. *J. Tissue Eng. Regen. Med.* 6(7), 570–578 (2012).
- 19 Gawlitta D, Van Rijen MH, Schrijver EJ, Alblas J, Dhert WJ. Hypoxia impedes hypertrophic chondrogenesis of human multipotent stromal cells. *Tissue Eng. Part A* 18(19–20), 1957–1966 (2012).
- 20 Henderson JH, Ginley NM, Caplan AI, Niyibizi C, Dennis JE. Low oxygen tension during incubation periods of chondrocyte expansion is sufficient to enhance postexpansion chondrogenesis. *Tissue Eng. Part A* 16(5), 1585–1593 (2010).
- 21 Kuo CK, Tuan RS. Mechanoactive tenogenic differentiation of human mesenchymal stem cells. *Tissue Eng. Part A* 14(10), 1615–1627 (2008).
- 22 Duan P, Pan Z, Cao L *et al.* The effects of pore size in bilayered poly(lactide-co-glycolide) scaffolds on restoring osteochondral defects in rabbits. *J. Biomed. Mater. Res. A* 102(1), 180–192 (2013).
- 23 Athanasiou KA, Rosenwasser MP, Buckwalter JA, Malinin TI, Mow VC. Interspecies comparisons of *in situ* intrinsic mechanical properties of distal femoral cartilage. *J. Orthop. Res.* 9(3), 330–340 (1991).
- 24 Buckwalter JA, Mankin HJ, Grodzinsky AJ. Articular cartilage and osteoarthritis. *Instr. Course Lect.* 54, 465–480 (2005).
- 25 Chan DD, Neu CP, Hull ML. *In situ* deformation of cartilage in cyclically loaded tibiofemoral joints by displacement-encoded mri. *Osteoarthritis Cartilage* 17(11), 1461–1468 (2009).
- 26 Kaab MJ, Ito K, Clark JM, Notzli HP. Deformation of articular cartilage collagen structure under static and cyclic loading. *J. Orthop. Res.* 16(6), 743–751 (1998).
- 27 Sophia Fox AJ, Bedi A, Rodeo SA. The basic science of articular cartilage: structure, composition, and function. *Sports Health* 1(6), 461–468 (2009).
- 28 Mansour JM. Biomechanics of cartilage. In: *Kinesiology: The Mechanics and Pathomechanics of Human Movement*. Oatis CA (Ed.). Lippincott Williams & Wilkins, PA, USA, 66–79 (2004).

- 29 Buckley MR, Bonassar LJ, Cohen I. Localization of viscous behavior and shear energy dissipation in articular cartilage under dynamic shear loading. *J. Biomech. Eng.* 135(3), 31002 (2013).
- 30 Linero I, Chaparro O. Paracrine effect of mesenchymal stem cells derived from human adipose tissue in bone regeneration. *PLoS ONE* 9(9), e107001 (2014).
- **Paracrine factors alone can be collected and applied as a therapeutic strategy in bone regeneration.**
- 31 Tandon S, Saha R, Rajendran R, Nayak R. Dental pulp stem cells from primary and permanent teeth: quality analysis. *J. Clin. Pediatr. Dent.* 35(1), 53–58 (2010).
- 32 Romanov YA, Darevskaya AN, Merzlikina NV, Buravkova LB. Mesenchymal stem cells from human bone marrow and adipose tissue: isolation, characterization, and differentiation potentialities. *Bull. Exp. Biol. Med.* 140(1), 138–143 (2005).
- 33 Trivanovic D, Kocic J, Mojsilovic S *et al.* Mesenchymal stem cells isolated from peripheral blood and umbilical cord Wharton's jelly. *Srp. Arh. Celok. Lek.* 141(3–4), 178–186 (2013).
- 34 Lai JH, Kajiyama G, Smith RL, Maloney W, Yang F. Stem cells catalyze cartilage formation by neonatal articular chondrocytes in 3D biomimetic hydrogels. *Sci. Rep.* 3, 3553 (2013).
- 35 Meretoja VV, Dahlin RL, Wright S, Kasper FK, Mikos AG. The effect of hypoxia on the chondrogenic differentiation of co-cultured articular chondrocytes and mesenchymal stem cells in scaffolds. *Biomaterials* 34(17), 4266–4273 (2013).
- 36 Mara CS, Duarte AS, Sartori A, Luzo AC, Saad ST, Coimbra IB. Regulation of chondrogenesis by transforming growth factor-beta 3 and insulin-like growth factor-1 from human mesenchymal umbilical cord blood cells. *J. Rheumatol.* 37(7), 1519–1526 (2010).
- 37 Mueller MB, Fischer M, Zellner J *et al.* Hypertrophy in mesenchymal stem cell chondrogenesis: effect of TGF-beta isoforms and chondrogenic conditioning. *Cells Tissues Organs* 192(3), 158–166 (2010).
- 38 Karlsson C, Brantsing C, Svensson T *et al.* Differentiation of human mesenchymal stem cells and articular chondrocytes: analysis of chondrogenic potential and expression pattern of differentiation-related transcription factors. *J. Orthop. Res.* 25(2), 152–163 (2007).
- 39 Day TF, Guo X, Garrett-Beal L, Yang Y. Wnt/beta-catenin signaling in mesenchymal progenitors controls osteoblast and chondrocyte differentiation during vertebrate skeletogenesis. *Dev. Cell* 8(5), 739–750 (2005).
- 40 Correa D, Somoza RA, Lin P *et al.* Sequential exposure to fibroblast growth factors (FGF) 2, 9 and 18 enhances HMSC chondrogenic differentiation. *Osteoarthritis Cartilage* 23(3), 443–453 (2014).
- 41 Garza-Veloz I, Romero-Diaz VJ, Martinez-Fierro ML *et al.* Analyses of chondrogenic induction of adipose mesenchymal stem cells by combined co-stimulation mediated by adenoviral gene transfer. *Arthritis Res. Ther.* 15(4), R80 (2013).
- 42 Li WJ, Chiang H, Kuo TF, Lee HS, Jiang CC, Tuan RS. Evaluation of articular cartilage repair using biodegradable nanofibrous scaffolds in a swine model: a pilot study. *J. Tissue Eng. Regen. Med.* 3(1), 1–10 (2009).
- 43 Ousema PH, Moutos FT, Estes BT *et al.* The inhibition by interleukin 1 of MSC chondrogenesis and the development of biomechanical properties in biomimetic 3D woven PCL scaffolds. *Biomaterials* 33(35), 8967–8974 (2012).
- 44 Zellner J, Mueller M, Krutsch W *et al.* Arthroscopic three dimensional autologous chondrocyte transplantation with navigation-guided cartilage defect size assessment. *Arch. Orthop. Trauma Surg.* 132(6), 855–860 (2012).
- 45 Khanarian NT, Jiang J, Wan LQ, Mow VC, Lu HH. A hydrogel-mineral composite scaffold for osteochondral interface tissue engineering. *Tissue Eng. Part A* 18(5–6), 533–545 (2012).
- 46 Mouthuy PA, El-Sherbini Y, Cui Z, Ye H. Layering PLGA-based electrospun membranes and cell sheets for engineering cartilage-bone transition. *J. Tissue Eng. Regen. Med.* doi: 10.1002/term.1765 (2013) (Epub ahead of print).
- 47 Liao J, Hu N, Zhou N *et al.* Sox9 potentiates BMP2-induced chondrogenic differentiation and inhibits BMP2-induced osteogenic differentiation. *PLoS ONE* 9(2), e89025 (2014).
- 48 Singh A, Goel SC, Gupta KK *et al.* The role of stem cells in osteoarthritis: an experimental study in rabbits. *Bone Joint Res.* 3(2), 32–37 (2014).
- **Confirms efficacy of direct injection of bone marrow-derived stem cells in treatment of osteoarthritis without the need for scaffolding.**
- 49 Vilar JM, Morales M, Santana A *et al.* Controlled, blinded force platform analysis of the effect of intraarticular injection of autologous adipose-derived mesenchymal stem cells associated to prgf-endoret in osteoarthritic dogs. *BMC Vet. Res.* 9, 131 (2013).
- 50 Orozco L, Munar A, Soler R *et al.* Treatment of knee osteoarthritis with autologous mesenchymal stem cells: a pilot study. *Transplantation* 95(12), 1535–1541 (2013).
- 51 Van Buul GM, Siebelt M, Leijts MJ *et al.* Mesenchymal stem cells reduce pain but not degenerative changes in a monoiodoacetate rat model of osteoarthritis. *J. Orthop. Res.* 32(9), 1167–1174 (2014).
- 52 Saulnier N, Viguier E, Perrier-Groult E *et al.* Intra-articular administration of xenogeneic neonatal mesenchymal stromal cells early after meniscal injury down-regulates metalloproteinase gene expression in synovium and prevents cartilage degradation in a rabbit model of osteoarthritis. *Osteoarthritis Cartilage* 23(1), 122–133 (2015).
- 53 Duval E, Bauge C, Andriamanalijaona R *et al.* Molecular mechanism of hypoxia-induced chondrogenesis and its application in *in vivo* cartilage tissue engineering. *Biomaterials* 33(26), 6042–6051 (2012).
- 54 Gasparotto VP, Landim-Alvarenga FC, Oliveira AL *et al.* A new fibrin sealant as a three-dimensional scaffold candidate for mesenchymal stem cells. *Stem Cell Res. Ther.* 5(3), 78 (2014).
- 55 Spoliti M, Iudicone P, Leone R, De Rosa A, Rossetti FR, Pierelli L. *In vitro* release and expansion of mesenchymal stem cells by a hyaluronic acid scaffold used in combination

- with bone marrow. *Muscles Ligaments Tendons J.* 2(4), 289–294 (2012).
- 56 Ahearne M, Kelly DJ. A comparison of fibrin, agarose and gellan gum hydrogels as carriers of stem cells and growth factor delivery microspheres for cartilage regeneration. *Biomed. Mater.* 8(3), 035004 (2013).
- 57 Chen YC, Chen RN, Jhan HJ *et al.* Development and characterization of acellular extracellular matrix scaffolds from porcine menisci for use in cartilage tissue engineering. *Tissue Eng. Part C Methods* doi:10.1089/ten.TEC.2015.0036 (2015) (Epub ahead of print).
- **Presents a new way to prepare acellular extracellular matrix and demonstrates its effectiveness as a scaffold to support tissue repair.**
- 58 Xu Y, Xu GY, Tang C *et al.* Preparation and characterization of bone marrow mesenchymal stem cell-derived extracellular matrix scaffolds. *J. Biomed. Mater. Res. B Appl. Biomater.* 103(3), 670–678 (2015).
- 59 Coburn JM, Gibson M, Monagle S, Patterson Z, Elisseff JH. Bioinspired nanofibers support chondrogenesis for articular cartilage repair. *Proc. Natl Acad. Sci. USA* 109(25), 10012–10017 (2012).
- 60 Guasti L, Vagaska B, Bulstrode NW, Seifalian AM, Ferretti P. Chondrogenic differentiation of adipose tissue-derived stem cells within nanocaged porous poly(lactide-co-glycolide) scaffolds: a new tool for nanomedicine. *Nanomedicine* 10(2), 279–289 (2014).
- 61 Peyton SR, Kalcioğlu ZI, Cohen JC *et al.* Marrow-derived stem cell motility in 3D synthetic scaffold is governed by geometry along with adhesivity and stiffness. *Biotechnol. Bioeng.* 108(5), 1181–1193 (2011).
- 62 Kum CH, Cho Y, Seo SH, Joung YK, Ahn DJ, Han DK. A poly(lactide) stereocomplex structure with modified magnesium oxide and its effects in enhancing the mechanical properties and suppressing inflammation. *Small* 10(18), 3783–3794 (2014).
- 63 Ravindran S, Gao Q, Kotecha M *et al.* Biomimetic extracellular matrix-incorporated scaffold induces osteogenic gene expression in human marrow stromal cells. *Tissue Eng. Part A* 18(3–4), 295–309 (2012).
- 64 Son YJ, Yoon IS, Sung JH *et al.* Porous hyaluronic acid/sodium alginate composite scaffolds for human adipose-derived stem cells delivery. *Int. J. Biol. Macromol.* 61, 175–181 (2013).
- 65 Moutos FT, Guilak F. Functional properties of cell-seeded three-dimensionally woven poly(epsilon-caprolactone) scaffolds for cartilage tissue engineering. *Tissue Eng. Part A* 16(4), 1291–1301 (2010).
- 66 Chicatun F, Pedraza CE, Muja N, Ghezzi CE, Mckee MD, Nazhat SN. Effect of chitosan incorporation and scaffold geometry on chondrocyte function in dense collagen type I hydrogels. *Tissue Eng. Part A* 19(23–24), 2553–2564 (2013).
- 67 Childs A, Hemraz UD, Castro NJ, Fenniri H, Zhang LG. Novel biologically-inspired rosette nanotube PLLA scaffolds for improving human mesenchymal stem cell chondrogenic differentiation. *Biomed. Mater.* 8(6), 065003 (2013).
- 68 Fernandez-Muinos T, Recha-Sancho L, Lopez-Chicon P, Castells-Sala C, Mata A, Semino CE. Bimolecular based heparin and self-assembling hydrogel for tissue engineering applications. *Acta Biomater.* 16, 35–48 (2015).
- 69 Ahn EH, Kim Y, Kshitiz *et al.* Spatial control of adult stem cell fate using nanotopographic cues. *Biomaterials* 35(8), 2401–2410 (2014).
- 70 Huang CC, Ravindran S, Yin Z, George A. 3D self-assembling leucine zipper hydrogel with tunable properties for tissue engineering. *Biomaterials* 35(20), 5316–5326 (2014).
- 71 Wang LS, Du C, Toh WS, Wan AC, Gao SJ, Kurisawa M. Modulation of chondrocyte functions and stiffness-dependent cartilage repair using an injectable enzymatically crosslinked hydrogel with tunable mechanical properties. *Biomaterials* 35(7), 2207–2217 (2014).
- **Adjusting injectable hydrogel stiffness regulates cell proliferation, biosynthesis of proteins, gene expression and has a direct impact on the success of defect repair.**
- 72 Florine EM, Miller RE, Liebesny PH *et al.* Delivering heparin-binding insulin-like growth factor 1 with self-assembling peptide hydrogels. *Tissue Eng. Part A* 21(3–4), 637–646 (2015).
- 73 Kopesky PW, Byun S, Vanderploeg EJ, Kisiday JD, Frisbie DD, Grodzinsky AJ. Sustained delivery of bioactive TGF-beta1 from self-assembling peptide hydrogels induces chondrogenesis of encapsulated bone marrow stromal cells. *J. Biomed. Mater. Res. A* 102(5), 1275–1285 (2014).
- 74 Guenther D, Oks A, Ettinger M *et al.* Enhanced migration of human bone marrow stromal cells in modified collagen hydrogels. *Int. Orthop.* 37(8), 1605–1611 (2013).
- 75 Skaalure SC, Dimson SO, Pennington AM, Bryant SJ. Semi-interpenetrating networks of hyaluronic acid in degradable PEG hydrogels for cartilage tissue engineering. *Acta Biomater.* 10(8), 3409–3420 (2014).
- 76 Hung CT, Mow VC. Biomechanics of articular cartilage. In: *Basic Biomechanics of the Musculoskeletal System*. Nordin M, Frankel VH. (Eds). Wolters Kluwer Health/Lippincott Williams & Wilkins, PL, USA, 60–101 (2012).
- 77 Juhasz T, Matta C, Somogyi C *et al.* Mechanical loading stimulates chondrogenesis via the PKA/CREB-Sox9 and PP2A pathways in chicken micromass cultures. *Cell Signal.* 26(3), 468–482 (2014).
- 78 Wang PY, Chow HH, Lai JY, Liu HL, Tsai WB. Dynamic compression modulates chondrocyte proliferation and matrix biosynthesis in chitosan/gelatin scaffolds. *J. Biomed. Mater. Res. B Appl. Biomater.* 91(1), 143–152 (2009).
- 79 Turunen SM, Han SK, Herzog W, Korhonen RK. Cell deformation behavior in mechanically loaded rabbit articular cartilage 4 weeks after anterior cruciate ligament transection. *Osteoarthritis Cartilage* 21(3), 505–513 (2013).
- 80 Han SK, Madden R, Abusara Z, Herzog W. *In situ* chondrocyte viscoelasticity. *J. Biomech.* 45(14), 2450–2456 (2012).
- 81 Jeon JE, Schrobback K, Meinert C, Sramek V, Hutmacher DW, Klein TJ. Effect of preculture and loading on expression of matrix molecules, matrix metalloproteinases, and cytokines by expanded osteoarthritic chondrocytes. *Arthritis Rheum.* 65(9), 2356–2367 (2013).

- 82 Wang QG, Nguyen B, Thomas CR, Zhang Z, El Haj AJ, Kuiper NJ. Molecular profiling of single cells in response to mechanical force: comparison of chondrocytes, chondrons and encapsulated chondrocytes. *Biomaterials* 31(7), 1619–1625 (2010).
- 83 Han SK, Wouters W, Clark A, Herzog W. Mechanically induced calcium signaling in chondrocytes *in situ*. *J. Orthop. Res.* 30(3), 475–481 (2012).
- 84 Campbell JJ, Blain EJ, Chowdhury TT, Knight MM. Loading alters actin dynamics and up-regulates cofilin gene expression in chondrocytes. *Biochem. Biophys. Res. Commun.* 361(2), 329–334 (2007).
- 85 Ofek G, Dowling EP, Raphael RM, McGarry JP, Athanasiou KA. Biomechanics of single chondrocytes under direct shear. *Biomech. Model. Mechanobiol.* 9(2), 153–162 (2010).
- 86 Leblanc KT, Walcott ME, Gaur T *et al.* Runx1 activities in superficial zone chondrocytes, osteoarthritic chondrocyte clones and response to mechanical loading. *J. Cell Physiol.* doi: 10.1002/jcp.24727 (2014) (Epub ahead of print).
- 87 Lee JH, Fitzgerald JB, Dimicco MA, Grodzinsky AJ. Mechanical injury of cartilage explants causes specific time-dependent changes in chondrocyte gene expression. *Arthritis Rheum.* 52(8), 2386–2395 (2005).
- 88 Perera PM, Wypasek E, Madhavan S *et al.* Mechanical signals control SOX-9, VEGF, and c-Myc expression and cell proliferation during inflammation via integrin-linked kinase, B-Raf, and ERK1/2-dependent signaling in articular chondrocytes. *Arthritis Res. Ther.* 12(3), R106 (2010).
- 89 Huang AH, Farrell MJ, Kim M, Mauck RL. Long-term dynamic loading improves the mechanical properties of chondrogenic mesenchymal stem cell-laden hydrogel. *Eur. Cell Mater.* 19, 72–85 (2010).
- 90 Haugh MG, Meyer EG, Thorpe SD, Vinardell T, Duffy GP, Kelly DJ. Temporal and spatial changes in cartilage-matrix-specific gene expression in mesenchymal stem cells in response to dynamic compression. *Tissue Eng. Part A* 17(23–24), 3085–3093 (2011).
- 91 Fuhrer R, Hofmann S, Hild N *et al.* Pressureless mechanical induction of stem cell differentiation is dose and frequency dependent. *PLoS ONE* 8(11), e81362 (2013).
- 92 Pelaez D, Arita N, Cheung HS. Extracellular signal-regulated kinase (ERK) dictates osteogenic and/or chondrogenic lineage commitment of mesenchymal stem cells under dynamic compression. *Biochem. Biophys. Res. Commun.* 417(4), 1286–1291 (2012).
- 93 Wang Y, Wang J, Bai D *et al.* Cell proliferation is promoted by compressive stress during early stage of chondrogenic differentiation of rat BMSCs. *J. Cell Physiol.* 228(9), 1935–1942 (2013).
- 94 Zhou S, Cui Z, Urban JP. Factors influencing the oxygen concentration gradient from the synovial surface of articular cartilage to the cartilage-bone interface: a modeling study. *Arthritis Rheum.* 50(12), 3915–3924 (2004).
- 95 Maes C, Araldi E, Haigh K *et al.* VEGF-independent cell-autonomous functions of HIF-1 α regulating oxygen consumption in fetal cartilage are critical for chondrocyte survival. *J. Bone Miner. Res.* 27(3), 596–609 (2012).
- 96 Zhu M, Feng Q, Bian L. Differential effect of hypoxia on human mesenchymal stem cell chondrogenesis and hypertrophy in hyaluronic acid hydrogels. *Acta Biomater.* 10(3), 1333–1340 (2014).
- 97 Merceron C, Vinatier C, Portron S *et al.* Differential effects of hypoxia on osteochondrogenic potential of human adipose-derived stem cells. *Am. J. Physiol. Cell Physiol.* 298(2), C355–C364 (2010).
- 98 Munir S, Foldager CB, Lind M, Zachar V, Soballe K, Koch TG. Hypoxia enhances chondrogenic differentiation of human adipose tissue-derived stromal cells in scaffold-free and scaffold systems. *Cell Tissue Res.* 355(1), 89–102 (2014).
- 99 Portron S, Merceron C, Gauthier O *et al.* Effects of *in vitro* low oxygen tension preconditioning of adipose stromal cells on their *in vivo* chondrogenic potential: application in cartilage tissue repair. *PLoS ONE* 8(4), e62368 (2013).
- 100 Boyette LB, Creasey OA, Guzik L, Lozito T, Tuan RS. Human bone marrow-derived mesenchymal stem cells display enhanced clonogenicity but impaired differentiation with hypoxic preconditioning. *Stem Cells Transl. Med.* 3(2), 241–254 (2014).
- 101 Kalpakci KN, Brown WE, Hu JC, Athanasiou KA. Cartilage tissue engineering using dermis isolated adult stem cells: the use of hypoxia during expansion versus chondrogenic differentiation. *PLoS ONE* 9(5), e98570 (2014).
- 102 Cicione C, Muinos-Lopez E, Hermida-Gomez T, Fuentes-Boquete I, Diaz-Prado S, Blanco FJ. Effects of severe hypoxia on bone marrow mesenchymal stem cells differentiation potential. *Stem Cells Int.* 2013, 232896 (2013).
- 103 Chen P, Tao J, Zhu S *et al.* Radially oriented collagen scaffold with SDF-1 promotes osteochondral repair by facilitating cell homing. *Biomaterials* 39, 114–123 (2015).
- 104 Mao H, Kawazoe N, Chen G. Cellular uptake of single-walled carbon nanotubes in 3D extracellular matrix-mimetic composite collagen hydrogels. *J. Nanosci. Nanotechnol.* 14(3), 2487–2492 (2014).
- 105 Sridhar BV, Brock JL, Silver JS, Leight JL, Randolph MA, Anseth KS. Development of a cellularly degradable PEG hydrogel to promote articular cartilage extracellular matrix deposition. *Adv. Healthc. Mater.* 4(5), 702–713 (2015).
- 106 Park H, Choi B, Hu J, Lee M. Injectable chitosan hyaluronic acid hydrogels for cartilage tissue engineering. *Acta Biomater.* 9(1), 4779–4786 (2013).
- 107 Walker KJ, Madhally SV. Anisotropic temperature sensitive chitosan-based injectable hydrogels mimicking cartilage matrix. *J. Biomed. Mater. Res. B Appl. Biomater.* doi: 10.1002/jbm.b.33293 (2014) (Epub ahead of print).
- 108 Snyder TN, Madhavan K, Intrator M, Dregalla RC, Park D. A fibrin/hyaluronic acid hydrogel for the delivery of mesenchymal stem cells and potential for articular cartilage repair. *J. Biol. Eng.* 8, 10 (2014).
- 109 Zahedmanesh H, Stoddart M, Lezuo P *et al.* Deciphering mechanical regulation of chondrogenesis in fibrin-polyurethane composite scaffolds enriched with human mesenchymal stem cells: a dual computational and experimental approach. *Tissue Eng. Part A* 20(7–8), 1197–1212 (2014).

- 110 Moutos FT, Estes BT, Guilak F. Multifunctional hybrid three-dimensionally woven scaffolds for cartilage tissue engineering. *Macromol. Biosci.* 10(11), 1355–1364 (2010).
- 111 Calikoglu Koyuncu AC, Gurel Pekozer G, Ramazanoglu M, Torun Kose G, Hasirci V. Cartilage tissue engineering on macroporous scaffolds using human tooth germ stem cells. *J. Tissue Eng. Regen. Med.* doi: 10.1002/term.1975. (2015) (Epub ahead of print).
- 112 Tsai MC, Hung KC, Hung SC, Hsu SH. Evaluation of biodegradable elastic scaffolds made of anionic polyurethane for cartilage tissue engineering. *Colloids Surf. B Biointerfaces* 125, 34–44 (2015).
- 113 Matsiko A, Gleeson J, O'Brien FJ. Scaffold mean pore size influences mesenchymal stem cell chondrogenic differentiation and matrix deposition. *Tissue Eng. Part A* 21(3–4), 486–497 (2014).
- 114 Kim IL, Khetan S, Baker BM, Chen CS, Burdick JA. Fibrous hyaluronic acid hydrogels that direct MSC chondrogenesis through mechanical and adhesive cues. *Biomaterials* 34(22), 5571–5580 (2013).
- 115 Kwon HJ, Yasuda K. Chondrogenesis on sulfonate-coated hydrogels is regulated by their mechanical properties. *J. Mech. Behav. Biomed. Mater.* 17, 337–346 (2013).
- 116 Bian L, Hou C, Tous E, Rai R, Mauck RL, Burdick JA. The influence of hyaluronic acid hydrogel crosslinking density and macromolecular diffusivity on human MSC chondrogenesis and hypertrophy. *Biomaterials* 34(2), 413–421 (2013).
- 117 Toh WS, Lim TC, Kurisawa M, Spector M. Modulation of mesenchymal stem cell chondrogenesis in a tunable hyaluronic acid hydrogel microenvironment. *Biomaterials* 33(15), 3835–3845 (2012).
- 118 Feng Q, Zhu M, Wei K, Bian L. Cell-mediated degradation regulates human mesenchymal stem cell chondrogenesis and hypertrophy in MMP-sensitive hyaluronic acid hydrogels. *PLoS ONE* 9(6), e99587 (2014).
- 119 Vinardell T, Rolfe RA, Buckley CT *et al.* Hydrostatic pressure acts to stabilise a chondrogenic phenotype in porcine joint tissue derived stem cells. *Eur. Cell Mater.* 23, 121–132; discussion 133–124 (2012).
- 120 Safshekan F, Tafazzoli-Shadpour M, Shokrgozar MA, Haghighipour N, Mahdian R, Hemmati A. Intermittent hydrostatic pressure enhances growth factor-induced chondroinduction of human adipose-derived mesenchymal stem cells. *Artif. Organs* 36(12), 1065–1071 (2012).
- 121 Ye R, Hao J, Song J *et al.* Microenvironment is involved in cellular response to hydrostatic pressures during chondrogenesis of mesenchymal stem cells. *J. Cell Biochem.* 115(6), 1089–1096 (2014).
- 122 Wang N, Chen J, Zhang G, Chai W. Chondrogenesis of passaged chondrocytes induced by different dynamic loads in bioreactor. *Zhongguo Xiu Fu Chong Jian Wai Ke Za Zhi* 27(7), 786–792 (2013).
- 123 Wang N, Grad S, Stoddart MJ *et al.* Particulate cartilage under bioreactor-induced compression and shear. *Int. Orthop.* 38(5), 1105–1111 (2014).